




Asian Journal of Nanoscience and Materials

Journal homepage: www.ajnanomat.com

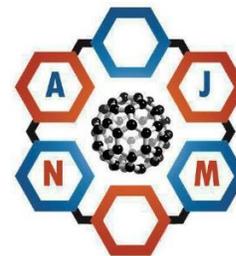

Review Article

Biodiesel production using a photocatalytic process: A review

Zahra Moafi^a, Zahra Abbasi^a, Mehdi Ahmadi^{b,c,*}

^a Faculty of Science, Ilam University, P.O. Box 69315516, Ilam, Iran

^b Environmental Technologies Research Center, Ahvaz Jundishapur University of Medical Sciences, Ahvaz, Iran

^c Department of Environmental Health Engineering, Ahvaz Jundishapur University of Medical Sciences, Ahvaz, Iran

ARTICLE INFORMATION

Received: 13 November 2022

Received in revised: 24 December 2022

Accepted: 09 January 2023

Available online: 13 January 2023

DOI: 10.26655/AJNANOMAT.2023.1.1

KEYWORDS

Biodiesel

Renewable

Non-Edible Oils


Photocatalytic

ABSTRACT

There is a growing demand for use of alternative clean energy as against fossil fuel. In trying to meet these demands, researchers are investigating various approaches towards delivering affordable clean energy from the abundant biomass in our environment, including biodiesel. Esterification of oils is one of the advanced methods of oil technology, which changes the main structure of glycerides without causing chemical changes in the fatty acid that forms the structure of triglycerides. Biodiesel is an alternative fuel that is renewable and produces less harmful gases than fossil fuels. Among the sources of biodiesel are vegetable oils and animal fat. The use of free solar light sources is significant for producing clean energy and reducing the economic costs of photocatalysts. In the present work, these issues have been addressed and the work done has been reviewed. The focus of this research is to examine the studies conducted to investigate the efficiency of biofuel production from edible and non-edible oils using photocatalysts. Studies have shown the production of biodiesel with high efficiency. High efficiency for biodiesel production from this method shows the future use of this fuel.

© 2023 by SPC (Sami Publishing Company), Asian Journal of Nanoscience and Materials, Reproduction is permitted for noncommercial purposes.

Graphical Abstract

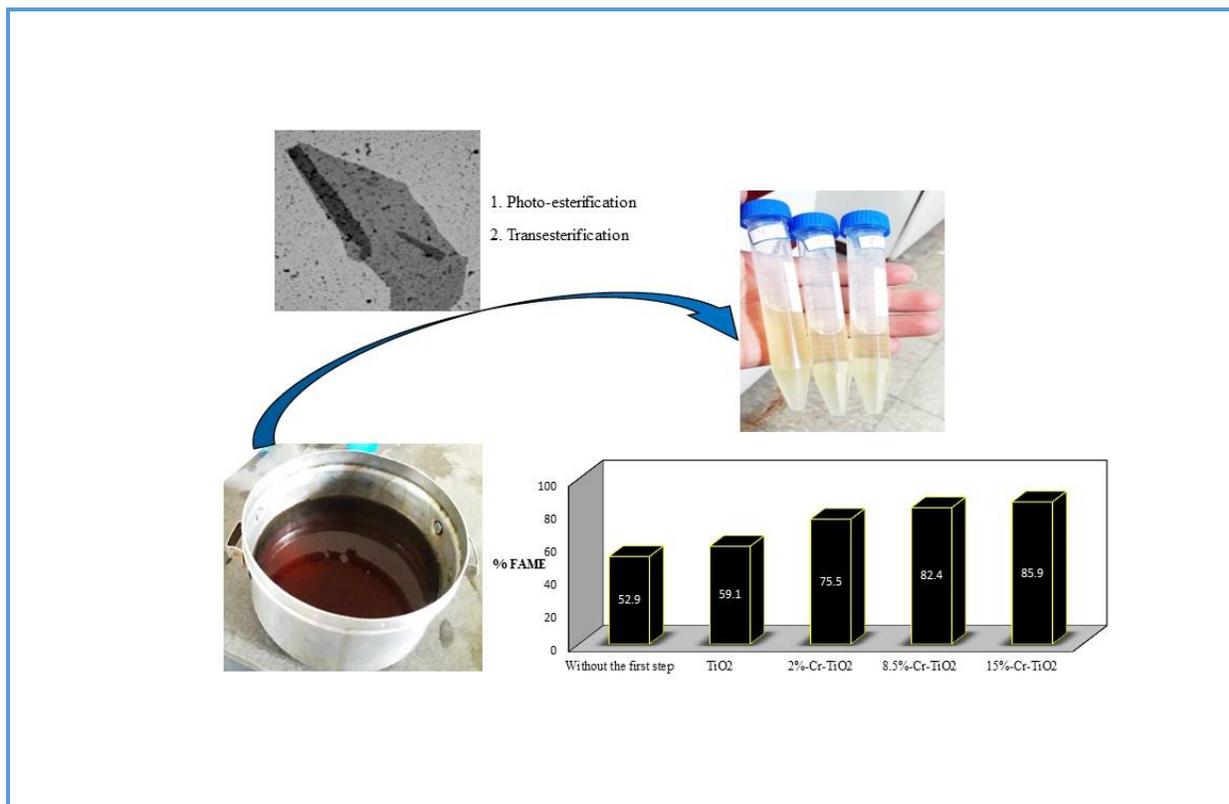

Introduction

Significant investments and studies have been conducted to provide adequate sources of alternative fuels in different countries due to the importance of the role of energy in the world, the non-renewability of fossil fuels and environmental issues arising from these fuels [1]. Biofuels such as biodiesel are obtained from edible and non-edible plants, animal fats, waste oils, etc. Today, countries pay special attention to biodiesel because the source of this fuel is animal and vegetable fats. Germany has already passed laws that allow the use of 5% biodiesel in diesel fuel. According to the standard, biodiesel is a mixture of long chain mono-alkyl esters of fatty acids resulting from the reaction of an alcohol with renewable lipids [2]. In most cases, the most important sources of non-renewable lipids are animal and vegetable oils.

Triglycerides are the main component of these oils. Therefore, in addition to the ester, another valuable product called glycerin is obtained as a result of this reaction. The standard specifications that a fuel product resulting from the reaction of alcohol with triglycerides (transesterification reaction) should have in order to be recognized as biodiesel are measured by ASTM 6751 standard. Over 95% of world biodiesel production uses edible oils as raw materials. The used oils include edible oils such as sunflower oil [3], soybean [4], palm oil [5], and others. Biodiesel produced from edible vegetables oils is called the first-generation biofuel. In addition, there are many concerns about using a potential food source as a biofuel. To solve this problem, the use of non-edible oils has also been studied. Among the non-edible oils for biodiesel production, *Jatropha Curcas*, and caoutchouc seed oils were studied.

Biodiesel produced from non-edible vegetable oils is called second generation biofuel [6]. Biodiesel, which is produced mostly from vegetable oils, is a mixture of mono-alkyl esters and is thought to replace diesel as a fuel.

Edible and non-edible vegetable oils can be used as raw material in biodiesel production. Biodiesel has been produced from a variety of vegetable oil sources such as soybean, sunflower, cottonseed, and so on [7-10].

However, the future of utilizing these edible oils is uncertain due to the increased global food demand. Moreover, the use of edible oils for biodiesel increases its production cost significantly. Biodiesel fuel is very similar to diesel fuel in terms of chemical properties, but unlike diesel fuel, it does not contain harmful substances such as sulfur, nitrogen, sulfate, and polycyclic aromatics. Figure 1 displays the molecular structure of biodiesel.

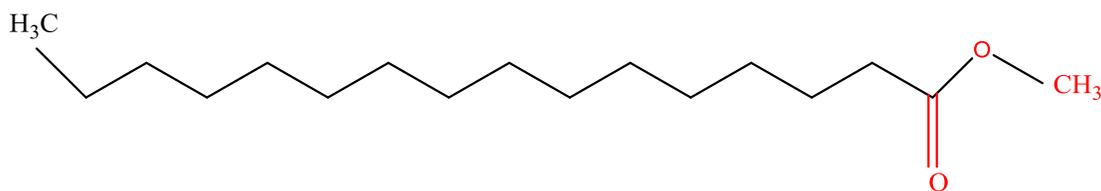


Figure 1. Molecular structure of biodiesel [11]

The use of biodiesel leads to a significant reduction in the number of unburnt hydrocarbons, carbon monoxide, and suspended particulate matter emitted from the exhaust. Nitrogen oxides from the biodiesel production process show a slight decrease or increase. Due to the presence of oxygen (about 11% wt) in the structure of biodiesel fuel, its combustion is complete, so the amount of carbon in suspended particles is decreased. Likewise, the absence of sulfur compounds in it is another reason for the compatibility of this fuel with the environment [11, 12]. Due to its excellent lubrication performance, biodiesel can effectively reduce the abrasion of engine components and increase engine service life. Biodiesel not only has a high cetane number and good combustion performance, but also has a good degradation that does damage human health [13]. In addition, biodiesel has a high flash point that is suitable for transportation and storage [14]. Biodiesel has good viscosity and high boiling point and cetane number. It is easy to use. It is biodegradable and non-toxic

and lacks aromatic substances [15, 16]. According to these properties, it is a suitable alternative for petroleum fuel that has been considered by many countries. The reaction efficiency of biodiesel production depends on the reaction conditions. The amount of free fatty acid in the oil sample, water, reaction temperature, type, amount of catalyst, alcohol to oil ratio, stirring speed, and reaction time are important parameters for biodiesel production [17]. In the following, some of the factors in the efficiency of biodiesel production will be examined.

Effect of free fatty acid and water

Free fatty acids and water in oily substances can significantly influence ester performance and glyceride conversion in the transesterification reaction with the base catalyst. All raw materials for biodiesel production such as oily raw materials, alcohol, and catalysts should be largely water-free. Prolonged exposure to atmospheric air of the base catalyst reduces the effect of the catalyst

through the contact of the catalyst with moisture and carbon dioxide in the air. In addition, the raw materials used in catalytic transesterification with bases should have less than 0.5% wt free fatty acid (FFA) [18]. The higher the acidity of the oil, the lower the conversion and efficiency of the transesterification. If FFA is present in large amounts in the initial oil, a base catalyst is needed to neutralize the FFA. The reaction between the base catalyst and the FFA leads to

the consumption of catalyst and the formation of soap and waters, which is called saponification (Figure 2). The water in the reaction hydrolyzes the glycerides to form soap and glycerol (Figure 3). Furthermore, water can enhance ester hydrolysis to form FFA, which reduces ester performance (Figure 4). Soap formed during the saponification increases the viscosity or gel formation, which interferences with the transesterification reaction as well as glycerol separation [19].

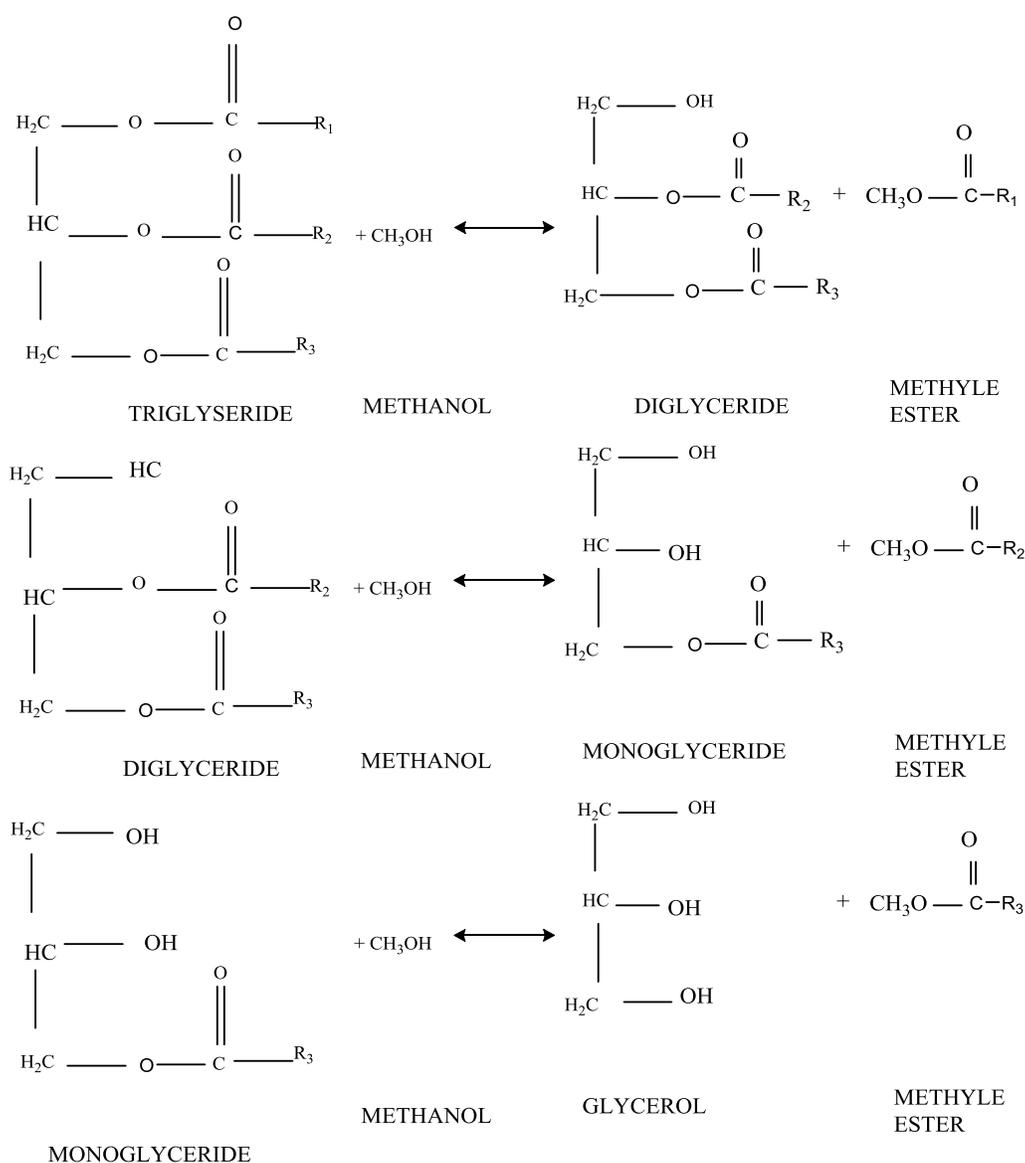


Figure 2. Step-by-step transesterification reactions

in the transesterification stage. Due to the reaction reversibility, excess alcohol is commonly used in the transesterification to promote the reaction toward the product. In general, 98% conversion is achievable in the ratio of 1:6 alcohol to oil for reactions performed with base catalyst, and increasing the alcohol used in the reaction does not increase the conversion efficiency [21]. The optimal ratio of alcohol to oil can vary depending on the oil quality and the type of oil used. It has been reported that a maximum of 92% of the conversion was obtained using a ratio of 1:10 methanol to oil for the production of biodiesel from Karanja oil [22].

Leung and Guo [23] reported that canola oil was esterified 98% by transesterification using a 1:6 alcohol to oil ratio. In cooking oil esterification, a 1:7 ratio of alcohol to oil was required to obtain 94% esterification.

In *Cynara Cardunculus L.* oil transesterification, the optimal ethanol to oil ratio was 1:12, while increasing the ethanol to oil ratio to 1:15 reduced esterification [24]. Rashid and Anwar [25] reported that further increase of alcohol used in transesterification of rapeseed oil beyond its optimal ratio (1:6) leads to the decrease in esterification. When too much alcohol is used in transesterification, the polarity of the reaction mixture increases, and thus it increases the solubility of glycerol again in the ester phase and causes an inverse reaction between the glycerol and the ester or glyceride. As a result, it reduces the esterification efficiency. Reactions containing acid catalysts use more alcohol than base catalysts. In some cases, an alcohol to oil ratio of 1:245 has been reported and up to 99% conversion was observed [26]. The type of alcohol used in the transesterification can affect the reaction efficiency. Methanol is mostly used in transesterification due to its economic benefits [18]. Disadvantages of using methanol

are the dependence on oil resources and lower solubility of glyceride in methanol. It has been reported that at least 3 minutes is required for mixing methanol with triglyceride in soybean oil methanolysis [27]. This time is about 2-3 minutes for methanolysis of soybean oil and sunflower oil [28, 29]. The insolubility of triglyceride in methanol has been reported due to mass transfer resistance or mass transfer limitation. To solve this problem, several methods have been used including the use of severe mechanical agitation, cosolvent [30], the use of supercritical conditions [31-33], and other techniques such as microwave [34, 35] and ultrasonic [36, 37]. Effort to improve triglyceride mass transfer has been investigated using the other alcohols such as ethanol, propanol, and butanol [38-41].

Biodiesel produced using ethanol is completely renewable. The main problem with methanolysis is the lower reactivity of ethoxide. If ethanol is used instead of methanol, the length of the carbon chain increases, which leads to a decrease in nucleophilicity and reactivity of the ethoxide compared to methoxide [42]. Lower polarity of ethanol has advantages and disadvantages in the transesterification process. On the one hand, lower polarity of ethanol reduces the initial mass resistance to methanolysis, and thus it increases the initial reaction rate. On the other hand, it improves the interaction of ester and glycerol in the presence of reaction catalyst and causes the process of saponification. Therefore, saponification occurs faster in ethanolysis and the concentration of soap is higher than methanolysis in the biodiesel production stage [43].

Effect of reaction time and temperature

In general, the reaction conversion efficiency increases with increasing reaction time. The reaction begins with two types of raw materials:

alcohol and oil. After beginning the reaction, diglyceride and monoglyceride are formed as reaction mediators and act as surfactants to increase the mass transfer of triglyceride to methanol. At this stage, the reaction mixture is one or two phases depending on the amount and types of alcohol used in the reaction and the reaction conditions. Glycerol is then formed as a by-product of the reaction and separated as an additional phase. If the reaction is catalyzed homogeneously, the glycerol separation often leads to the catalyst dissolution in the glycerol phase, which reduces the catalyst concentration in the reaction mixture, and thus slows down the reaction rate. Reaction rate and rate constant are used in kinetic researches to evaluate the rate of reaction progress. These kinetic parameters are sometimes evaluated based on the shunt reaction mechanism in which three moles of triglyceride react with three moles of alcohol to produce three moles of ester and one mole of glycerol [28].

Although kinetic models can be simplified using the shunt reaction mechanism, it is unlikely that three methanol molecules simultaneously attack the triglyceride molecule to form the three methyl ester molecules. The reaction of converting triglyceride into diglyceride is often a rate-limiting step that controls the overall reaction kinetics. Transesterification is highly dependent on the reaction temperature and more efficient at higher temperatures. Higher temperatures lead to more energy in the reacting molecules, which can lead to faster molecular vibration and movement. Therefore, reacting molecules have a better chance of colliding with each other. In the kinetically controlled region, the temperature dependence of the reaction rate is often used to calculate the reaction activation energy by plotting the constant logarithm of the velocity versus the reaction temperature [44] known as Arrhenius equation.

$$K = A \exp \left[\frac{-E_a}{RT} \right] \quad 1$$

Where, K is the rate constant, A is a pre-exponential factor, E_a is the activation energy, R is gas constant, and T is reaction temperature.

Activation energy is the minimum energy required to perform the reaction. If the reaction temperature increases, the rate constant also increases. Therefore, the reaction proceeds at a faster rate. Homogeneous transesterification with the base catalyst can be performed at a temperature lower than the room temperature. Higher temperatures are commonly used, especially when an acid catalyst is used. However, the reaction temperature should be less than the boiling point of the corresponding reactant alcohol, which is 65 °C for methanol and 78 °C for ethanol. High temperature up to 220 °C is usually required to achieve the optimum efficiency of the reaction involving the acid catalyst.

If the reaction takes place at temperatures above the boiling point of the reactant alcohol, pressure should be applied to the reaction mixture to keep the reactant alcohol in the liquid phase.

Effect of catalyst type

For the biodiesel synthesis from edible and non-edible oils, in addition to enzymes, two types of homogeneous or heterogeneous acid and base catalysts are used. Homogeneous catalysts are difficult to recover and lead to waste generation. Today, the use of heterogeneous catalysts has become more common so that the catalyst can be easily recovered after biodiesel production. The most common method for biodiesel synthesis is through the transesterification reaction, in which a catalytic chemical reaction including vegetable oil and alcohol is used to produce the alkyl esters of fatty acids and glycerol [17]. Triglycerides, as the main component of

vegetable oil, contain three long-chain fatty acids that are converted into the structure of esterified glycerol. When triglycerides react with alcohol (such as methanol), three fatty acid chains are removed from the glycerol chain and combined with methanol to produce fatty acid methyl esters (FAME). Glycerol is produced as a by-product. The type of catalyst is one of the most important parameters in the transesterification reaction. The choice of catalyst is an important step in determining the percentage of biodiesel production, and depends on the type and quality of raw materials.

Most commercial processes use base catalysts due to their high reaction efficiency, short reaction time and low reaction temperature [6]. Homogeneous base catalysts such as NaOH and KOH are the most active species for this purpose under normal conditions [45]. A base catalyst process can produce a biodiesel product with high purity and better efficiency in a short time (30-60 minutes) [46]. However, it is very sensitive to the reactants purity. It is clear that humidity and high FFA content of vegetable oils are important parameters in catalytic esterification reactions [47]. The FFA presence leads to the soap formation and reduces the efficiency of biodiesel production [48]. On the other hand, homogeneous acid catalysts have been used for this purpose, but require longer reaction times compared to base transesterification processes. Acid catalysts are commonly used for oils with high FFA content. This method requires high amount of alcohol, high pressure (170-180 KPa), and expensive stainless-steel equipment [49]. The use of an acid catalyst not only requires a long reaction time, but also produces acidic wastewater and corroded equipment [50].

In the production of industrial biodiesel, the two-stage method of acid and base catalyst is

used due to the presence of fatty acids. In the first stage, an esterification reaction is performed using an acid catalyst and the amount of free fatty acid is reduced. In the second stage, the base catalyst is used in the transesterification to increase the efficiency and control the test conditions. Recent studies showed that a heterogeneous photocatalytic process may be performed to efficiently esterify fatty acids without the problems of an acid catalyst. The first research was conducted by Corro *et al.* in 2013 [51]. They used ZnO/SiO₂ photocatalyst to esterify the FFAs in *Jatropha Curcas* oil, which has a fatty acid content of over 18%.

Photocatalyst in biodiesel synthesis

Three important methods have been developed to replace vegetable oils as diesel fuel including pyrolysis, microemulsion, and transesterification. Transesterification, also called alcoholysis, is the reaction of a fat or oil with an alcohol to form esters and glycerol. A catalyst is often used to improve reaction rate and efficiency. Due to the reversibility of the reaction, excess alcohol is used to shift the balance towards the products. Primary and secondary aliphatic alcohols with 1-8 carbons are used for this purpose. These alcohols include methanol, ethanol, propanol, and butanol. Methanol and ethanol have been most used due to their low cost and chemical and physical benefits (short chain length) [51]. The transesterification reaction is performed according to the following equations.

The kinetic equations for the transesterification reactions are, respectively, shown below for all reaction materials.

$$\begin{aligned}
 -\frac{d[TG]}{dt} &= +K_1[TG][A] - K_2[DG][E] \\
 -\frac{d[DG]}{dt} &= -K_1[TG][A] + K_2[DG][E] \\
 &\quad + K_3[DG][A] - K_4[MG][E]
 \end{aligned}$$

$$\begin{aligned}
 -\frac{d[MG]}{dt} &= -K_3[DG][A] + K_4[MG][E] \\
 &\quad + K_5[MG][A] - K_6[GL][E] \\
 -\frac{d[GL]}{dt} &= -K_5[MG][A] + K_6[GL][E] \\
 -\frac{d[B]}{dt} &= -K_1[TG][A] + K_2[DG][E] \\
 &\quad - K_3[DG][A] + K_4[MG][E] \\
 &\quad + K_5[MG][A] - K_6[GL][E] \\
 -\frac{d[A]}{dt} &= +\frac{d[B]}{dt}
 \end{aligned}$$

Where, TG is triglyceride, DG is diglyceride, MG is monoglyceride, GL is Glycerol, and A is alcohol and B is biodiesel.

Heterogeneous catalysts are inexpensive efficient processes for biodiesel production by reduction free fatty acids (FFA) in oil. Sunlight is an inexpensive and environmentally friendly

technology that makes it economical to use. The main mechanism to explain the performance of heterogeneous photocatalysts in biodiesel production was presented by Corro *et al.* [51] which is as follows:

1- When a heterogeneous photocatalyst is exposed to sunlight, electron pairs form a hole that transfer to the surface of the photocatalyst and interact with surrounding molecules.

2- Free electrons and holes are transferred to the surrounding molecules, and convert the molecules into free radicals.

3- The molecules around methanol and FFA are in the oil, which are irradiated during the heterogenous photocatalyst esterification with methanol and FFA. The photo- esterification process is displayed in the following Figure 6.

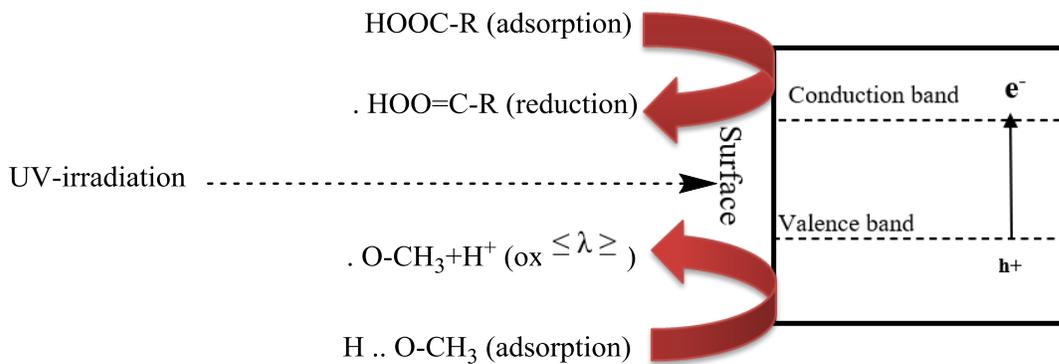


Figure 6. Photo- esterification mechanism

With UV- irradiation, the esterification process is performed in the following steps:


1- Transfer of methanol (CH₃OH) and FFA (HOOC-R) to the photocatalyst surface. This step can be improved using optimal stirring conditions in the reenactor.

2- Adsorption of methanol and FFA in the photocatalyst surface


3- Thg reaction takes place in the adsorbed phase on the photocatalyst surface during the following steps:

a) The UV photon collides with a photocatalyst to create an electron-hole.

b) Due to the high oxidizing potential, the holes can react with the adsorbed materials on the catalyst surface to form hydrogen ions (H⁺) and CH₃O radicals.



C) Hoo = C- R radical is then formed by the oxidation of HOOC- R absorbed on the catalyst surface by the generated \bar{e} .



4- The formed H^+ , CH_3O , and $HOO = C-R$ react together and then the intermediate and final product are formed.

5- Water and fatty acid methyl ester is desorbed during photo esterification.

6- Transfer of products from the catalyst surface to the liquid phase. This step can be improved by the optimal stirring conditions in the reactor.

In recent research, the effect of different parameters on the photocatalyst efficiency was investigated in the biodiesel production process.

So far, various studies have been conducted on acid and base catalysts to produce biodiesel, but a few studies have been reported on photocatalysts and waves in biodiesel production. We refer to these studies in the following.

The use of vegetable oils was introduced in the early 1980s as a competitive source of gasoline. The advantages of vegetable oils as biofuels include breadth of application, ease of access, renewability, high heat content, lower aromatic content, and biodegradability. The energy supply issues prompted special attention to this fuel, but its commercial production did not begin until the late 1990s.

Mengli *et al.* synthesized highly active as well as reusable La^{3+} and $ZnO-TiO_2$ photocatalyst by sol-gel method. In this research, edible oil wastes were used in a two-stage method. In the first stage, under ultraviolet irradiation, photocatalytic esterification of $La^{3+}/ZnO-TiO_2$ ethanol with free fatty acids was studied. In the second step, NaOH was used as the base catalyst for the transesterification of triglycerides with ethanol. At 35 °C, the molar ratio of ethanol to

oil was 1:12, the amount of catalyst was 4 wt%, the UV-irradiation time was 3 hours, and the FFA conversion percentage was 96.14% [52].

Young-Moo *et al.* (2010) investigated the esterification of free fatty acids in vegetable oils using WO_3/ZrO_2 heterogeneous catalyst. In this research, catalyst characterization was performed by BET, XRD, and FTIR methods. 10-30 wt% of WO_3 was studied on ZrO_2 surface. 78, 93 and 89% efficiency were seen in the presence of 10, 20, and 30% of WO_3 . The effect of temperature was studied on the efficiency of reaction. In 2 hours of reaction time, the conversion efficiency increased from 93 to 98% with increasing temperature from 75 to 200 °C [53].

Mazzocchia *et al.* (2004) investigated the transesterification of triglyceride to fatty acid methyl esters in the presence of a heterogeneous catalyst using microwaves. They found that the microwave method significantly reduced reaction time [54].

Lertsathapornsuk *et al.* (2005) studied the biodiesel production from three types of coconut oil, rice husk, and palm oil. They used microwave power of 800 watts and achieved the highest conversion rate in the sodium hydroxide 1% as a catalyst and a molar ratio of alcohol to oil of 1:9, and in 30s. In 30 seconds, conversion rates of 100, 94, and 83% were obtained for coconut oil, rice husk, and palm [55].

Corro *et al.* (2017) reported the biodiesel production from frying oil waste by a two- step process. In the first step, free fatty acids in the oil were esterified with methanol using a photocatalytic process, a semiconductor composite of Cr/SiO_2 and Solar radiation as a

light source. In the second step, transesterification of triglycerides with methanol was performed by thermal activation using solar radiation as a light source and NaOH. It was shown that the biodiesel obtained from this process has all the international requirements for application as a fuel [56].

Oloruntoba (2016) studied the efficacy of ZnO/SiO₂ photocatalyst in the production of biodiesel with the help of waste oil [57].

Jitputti *et al.* used several different ZrO₂/SO₄²⁻, ZrO₂SnO₂/SO₄²⁻, ZnO, KNO₃/ZrO, and KL/KNO₃ catalysts for the transesterification reaction of palm kernel oil and coconut oil. The results showed that ZrO₂/SO₄²⁻ had the highest performance compared to the other catalysts [58].

Chai *et al.* (2012) used Pt nanoparticles and g-C₃N₄ nanolayers to investigate the photocatalytic activity of TiO₂ in the visible region. In this research, urea precursor was used for the synthesis of g-C₃N₄, and the thickness of the synthesized g-C₃N₄ plates was 10 nm. In this research, it was observed that if Pt-TiO₂ and g-C₃N₄ are used in a ratio of 70 to 30, the maximum photocatalyst activity will be obtained for H₂ production [59].

Caixia Feng *et al.* (2014) studied the Ag₂CO₃ effect on the amount of photocatalytic activity of TiO₂ in the degradation process. In this research, Ag₂CO₃/P25 and Ag₂CO₃/TiO₂ were synthesized as a photocatalyst. The photocatalytic activity of these two composites was studied using oxidation-reduction reaction of propylene under visible light. Ag₂CO₃ was considered as a reference. Systems I and II were used. System I used a glass reactor with a Xenon lamp and system II used a quartz reactor with a Xenon lamp. In system I, the light intensity was about 9 m.w.cm⁻². In system II, the light intensity was 40 m.w.cm⁻². In system I, the highest efficiency was related to the Ag₂CO₃/TiO₂ composite, which removed about 90% of

propylene within 4 hours of irradiation, while Ag₂CO₃/P25 showed only 35% degradation. In system II, both synthesized composites of Ag₂CO₃/P25 and Ag₂CO₃/TiO₂ reported about 90% removal [60].

Weilin Wang *et al.* (2017) used a one-step method to synthesize sulfur-doped TiO₂ nanolayer photocatalyst on reduced graphene oxide (TiO₂-S/rGO). The results showed that doping with sulfur decreased the TiO₂ gap band. They found that the presence of rGO in the structure of this photocatalyst increases electron transfers and electron-hole separation, which results in an increase in photocatalyst efficiency [61].

Dong *et al.* (2017) synthesized a three-component heterogeneous g-C₃N₄ photocatalyst modified with nanolayer TiO₂ and ZnO. To study the efficiency of the synthesized photocatalyst, they used the degradation of p-toluene sulfonic acid (p-TSA) in the visible region. For the synthesis of modified g-C₃N₄, HNO₃ acid solution was used by thermal solvent method. Results showed that g-C₃N₄ modification increases the surface area from 8.175 m².g⁻¹ to 21.83 m².g⁻¹. The energy gap of modified g-C₃N₄ decreased from 2.71 eV to 2.68 eV, as compared with unmodified g-C₃N₄. By increasing the surface area and decreasing the energy gap, an increase in the degradation rate was observed [62].

Secula *et al.* (2008) investigated the response surface model and simulation of the degradation of dye effluent containing Reactive black 5 (RB5) azo dye using CCD method. The findings showed that the model was the second order, which was obtained during 16 experiments proposed by the software at the optimal conditions at the initial concentration of TiO₂ = 0.458 g. L⁻¹, Fe³⁺ = 40.243 mg. L⁻¹, and H₂O₂ = 825.3 mg. L⁻¹. The maximum dye degradation was 99.3% [63].

In research aimed at optimizing glucose-sulfonate acid catalyst for palm oil esterification reaction, Lokman *et al.* used the RSM method and CCRD model. In this research, a one-step reaction was performed in a reflux system at 65 °C. RSM method takes into account the relationship among three variables that significantly affect FFA conversion. These variables include alcohol to oil molar ratio, loaded catalyst concentration, and reaction time. The results showed that the catalyst concentration parameter had the highest effect on the conversion rate and yield efficiency. The optimum conditions were reported as 94.5% FFA conversion and 92.4% biodiesel efficiency using RSM method [63].

Conclusion

Biodiesel has different properties used to measure fuel quality and capabilities. To determine the quality of produced biodiesel, the characteristics of biodiesel fuel have been checked based on ASTM standards and the results were compared with the standard. Oil is an economic material for biodiesel production. The research was done using cheap sources of oil. Oxidation derivatives such as various acids are formed during the heating of oil. The formation of such compounds leads to an increase in the viscosity and acid number of oil. Due to this increase in acid number, the yield of biodiesel produced from waste oil is lower than that of fresh oil. The findings show that the biodiesel performance is reciprocally related to the acid number of the primary oil. However, it is possible to use the waste oil used for transesterification by adding an esterification step with photocatalysts. Photocatalysts are promising catalysts in the production of biodiesel fuel due to their efficiency in the light presence. Heterogeneous photocatalysts are separated from the reaction solution by

filtration. Photocatalysts with magnetic properties also have the ability to separate the reaction with a magnet. These types of catalysts have shown high recovery capability. Reuses of photocatalysts reduce the cost of repeated use of acid and base catalysts for the biodiesel production. The results of the research have shown that the esterification step in the presence of a photocatalyst reduces free fatty acids and will increase the efficiency of biodiesel production.

Disclosure Statement

No potential conflict of interest was reported by the authors.

References

- [1]. Shahbazi M.R., Khoshandam B., Nasiri M., Ghazvini, M. *J. Taiwan Inst. Chem. Eng.*, 2012, **43**:504 [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [2]. Luque, R., Lovett, J.C., Datta, B., Clancy, J., Campelo, J.M., Romero, A.A. *Energ Environ. Sci.*, 2010, **3**:1706 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [3]. Raviteja S., Satish P., Prasanna Y.R.K., Prasanna Kumar V.V. *Innovations in Mechanical Engineering*; Springer: Singapore, 2022, pp. 391-400 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [4]. Colombo K., Ender L., Santosb M.M., Chivanga Barros A.A. *S. Afr. J. Chem. Eng.*, 2019, **28**:19 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [5]. Farobie O., Hartulistiyoso E. *Bio. Energy Res.*, 2022, **15**:93 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [6]. Schlick M.L., Hanna M.A., Schinstock J.L. *Trans. ASAE*, 1988, **31**:1345 [[Google Scholar](#)]

- [7]. Ruhul A.M., Kalam M.A., Masjuki H.H., Fattah I.M.R., Reham S.S., Rashed M.M. *RSC Adv.*, 2015, **5**:101023 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [8]. Zahan K.A., Kano M. *Energies*, 2018, **11**:2132 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [9]. Abomohra A.F., Elsayed M., Esakkimuthu S., El-Sheekh M., Hanelt D. *Prog. Energy Combust. Sci.*, 2020, **81**:100868 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [10]. Kakati J., Gogoi T.K., Pakshirajan K. *Energy Convers. Manage.*, 2017, **135**:281 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [11]. Kegl B. *Energy Fuels*, 2006, **20**:1460. [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [12]. Pasqualino J.C., Montane D., Salvado J. *Biomass Bioenergy*, 2006, **30**:874 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [13]. Neff W.E., Ei-Agaimy M.A., Mounts T.L. *J. Am. Oil Chem. Soc.*, 1994, **71**:1111 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [14]. Smith B., Greenwell H.C. *Energy Environ. Sci.*, 2009, **2**:262 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [15]. Meher L.C., Sagar D.V., Naik S.N. *Renewable Sustainable Energy Rev.*, 2006, **10**:248 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [16]. Mag T. *Canola seed and oil processing. Canola Council of Canada* [[Google Scholar](#)], [[Publisher](#)]
- [17]. Freedman B., Pryde E.H., Mounts T.L. *J. Am. Oil Chem. Soc.*, 1984, **61**:1638
- [18]. Karmee S.K., Chadha A. *Bioresour. Technol.*, 2005, **96**:1425 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [19]. Leung D., Guo Y. *Fuel Process. Technol.*, 2006, **87**:883 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [20]. Enciner J.M., Gonzalez J.F., Rodriguez J.J., Tajedor A. *Energy Fuels*, 2002, **16**:443 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [21]. Rashid U., Anwar F. *Fuel*, 2008, **87**:265 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [22]. Zheng S., Kates, M., Dubé, M.A., McLean, D.D. *Biomass Bioenergy*, 2006, **30**:267 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [23]. Zhou W., Boocock D. *J. Am. Oil Chem. Soc.*, 2006, **83**:1041 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [24]. Freedman B., Butterfield R.O., Pryde E.H. *J. Am. Oil Chem. Soc.*, 1986, **63**:1375 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [25]. Mittelbach M., Trathnigg B. *Lipid/Fett.*, 1990, **92**:145 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [26]. Boocock D., Konar S.K., Mao V., Sidi H. *Biomass Bioenergy*, 1996, **11**:43 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [27]. Saka S., Kusdiana D. *Fuel*, 2001, **80**: 225 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [28]. Sherbiny E.I., Refaat S.A., Sheltawy E. *J. Adv. Res.*, 2010, **1**:309 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [29]. Kumar R., Kumar G.R., Chandrashekar N. *Bioresour. Technol.*, 2011, **102**:6617 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [30]. Colucci J.A., Borrero E.E., Alape F. *J. Am. Oil Chem. Soc.*, 2005, **82**:525 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [31]. Singh A.K., Fernando S.D., Hernandez R. *Energy Fuels*, 2007, **21**:1161 [[Google Scholar](#)]
- [32]. Lang X., Dalai A.K., Bakhshi N.N., Reaney M.J., Hertz P.B. *Bioresour. Technol.*, 2001, **80**:53 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [33]. Sridharan R., Mathai I.M. *J. Sci. Indust. Res.*, 1974, **33**:178 [[Google Scholar](#)]

- [34]. Mendow G., Veizaga N.S., Querini CA. *Bioresour. Technol.*, 2011, **102**:6385 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [35]. Sophia T., Maria, V., Ioannis P. *Appl. Chem. Engin.*, 2019, 1
- [36]. Dmytryshyn S.N., Dalai A.K., Chaudhari S.T., Misha H.K., Reaney M.J. *Bioresour. Technol.*, 2004, **92**:55 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [37]. Muniyappa P.R., Brammer S.C., Nouredini H. *Bioresour. Technol.*, 1996, **56**:19 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [38]. Giusy L., Giovanni L., Jeanette B. *Springer Nature*, 2016
- [39]. Dupont J., Suarez P.A.Z., Meneghetti M.R., Meneghetti S.M.P. *Energy Environ. Sci.*, 2009, **2**:1258 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [40]. Saka S., Isayama Y., Ilham Z., Jiayu X. *Fuel*, 2010, **89**:1442 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [41]. Tashtoush G.M., Al-Widyan M.I., Al-Shyoukh A.O. *Energy Convers. Manag.*, 2004, **45**:2697 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [42]. Al-Widyan M.I., Al-Shyoukh A.O. *Bioresour. Technol.*, 2002, **85**:253 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [43]. Corro G., Pal U., Tellez N. *Appl. Catal. B: Environ.* 2013, **129**:39 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [44]. Hossein A.E., Alireza S.Gh., Hossein T., Samare R. *Chem. Mater.*, 2017, **29**:8594 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [45]. Pelaez M., Nolan N. T., Pillai S.C., Seery M.K., Falaras P., Kontos A.G., Dunlop P.S., Hamilton J.W., Byrne J.A., O'shea K., Entezari M.H., Dionysiou D.D. *Appl. Catal. B: Environ.*, 2012, **12**:331 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [46]. Nolan N.T., Seery M.K., Pillai S.C. *J. Phys. Chem. C*, 2009, **113**:16151 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [47]. Hu Y., Tsai H.L., Huang C.L. *Europ. Ceram. Soc.*, 2003, **23**:691
- [48]. Asahi R., Taga Y., Mannstadt W., Freeman A. *Phys. Rev. B: Condens. Matter.*, 2000, **61**:7459 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [49]. Wisitsoraat A., Tuantranont A., Comini E., Sberveglieri G., Wlodarski W. *Thin Solid Films.*, 2009, **517**:2775 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [50]. Sajjan C.P., Wageh S., Al-Ghamdi A., Yu J., Cao S. *Nano Res.*, 2016, **9**:3 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [51]. Guo M., Jiang W., Chen C., Qu S., Lu J., Yi W., Ding J., *Energy Convers. Manag.*, 2021, **229**:113745 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [52]. Park Y.M., Lee J. Y., Chung S.H., Park I.S., Lee S.Y., Kim D.K., Lee J.S., Lee K.Y. *Bioresour. Technol.*, 2010, **101**:59 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [53]. Mazzocchia C., Kaddouri A., Nannicini R. *C. R. Chim.*, 2004, **7**:601 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [54]. Lertsathapornsuk V., Ruangying P., Pairintra R., Krisnangkura K. *Proceedings of the 1st conference on energy network*, 2005 [[Google Scholar](#)]
- [55]. Corro G., Sánchez N., Palb U., Cebadaa S., Luis J., Fierro G. *Appl. Catal. B: Environ.*, 2017, **203**:43 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [56]. Gadin J.M., Afolabi E.A., Kovo A.S., Abdulkareem A.S., Oloruntoa James M. *Biofuels*, 2022, 1 [[CrossRef](#)], [[Google Scholar](#)], [[Publisher](#)]
- [57]. Jitputti J., Kitiyanan B., Rangsunvigit P., Bunyakiat K., Attanatho L. *Chem. Eng. J.*, 2006,

- 116:61 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [58]. Chai B., Tianyou P., Jing M., Kan L., Ling Z. *Phys. Chem. Chem. Phys.*, 2012, **14**:16745 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [59]. Feng C., Li G., Ren P., Wang Y., Huang X., Li, D. *Appl.Catal. B: Environ.*, 2014, **158**:224 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [60]. Wang W., Wang Z., Liu J., Luo Z., Suib S.L., He P., Ding G., Zhang Z., Sun L. *Sci. Rep.*, 2017, **7**:46610 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [61]. Dong J., Han Y., Hongbing Y. *Comput. Biol. Med.* 2017, **85**:1 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [62]. Secula M.S., Suditu G.D., Poullos I., Cojocaru C.I. *Chem. Eng. J.*, 2008, **141**:18 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [63]. Lokman I. M., Rashid U., Taufiq-Yap Y. H. *Chinese J. Chem. Eng.*, 2015, **23**:1857 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]

How to cite this manuscript: Zahra Moafi, Zahra Abbasi, Mehdi Ahmadi*. Biodiesel production using a photocatalytic process: A review. *Asian Journal of Nanoscience and Materials*, 2023, 6(1), 1-15. DOI: 10.26655/AJNANOMAT.2023.1.1