

FULL PAPER

Removal of Pb (II) from aqueous solution by gel combustion derived nano Co₃O₄- ZnO

Iran Sheikhshoae^{a,*}, Azimeh Rezazadeh^{a,b}, Samaneh Ramezani^{a,b}

^aDepartment of Chemistry, Shahid Bahonar University of Kerman, Kerman, 76175, Iran


^bYoung Research Society, Shahid Bahonar University of Kerman, Kerman, Iran.

Received: 10 April 2018, Revised: 11 August 2018 and Accepted: 19 August 2018.

ABSTRACT: Nano Co₃O₄/ZnO have been successfully synthesized by a simple and green gel combustion method followed by calcination at 600 o C. Sugar was used as fuel for combustion in this work. The nano Co₃O₄-ZnO were characterized by X-ray diffraction (XRD), Energy Dispersive X-Ray analysis (EDAX) and Scanning electron microscopy (SEM). Co₃O₄-ZnO was applied as an adsorbent to remove lead from aqueous solution. EDAX strongly proved the adsorption of lead on the surface of Co₃O₄-ZnO adsorbent. By increasing the amount of ZnO on the structure of the Co₃O₄-ZnO samples, the adsorption of Pb²⁺ on the surface increased too. The SEM images also help the confirmation of lead adsorption on the surface of as synthesized samples. The concentrations of remained Pb²⁺ ions were also measured by atomic absorption spectroscopy (AAS) and reported in the terms of removal efficiency.

KEYWORDS: Gel combustion; Adsorption; Lead removal; Nanosized Co₃O₄/ZnO.

GRAPHICAL ABSTRACT:

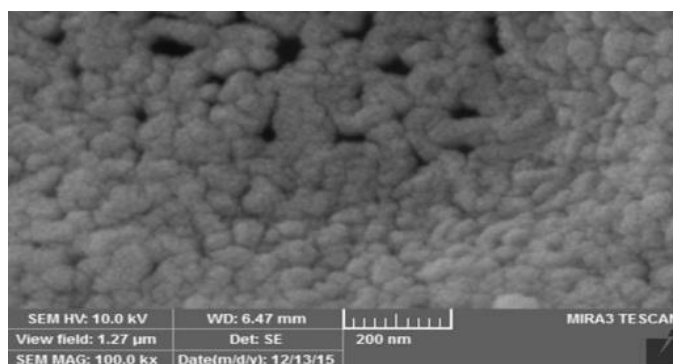

In this study, we demonstrated the synthesis and characterization of a new composite Co₃O₄/ZnO nanostructure by a Gel combustion method. The results show this compound exhibits an enhanced high adsorption capacity to the Pb(II) ions.

1. Introduction

By increasing heavy metals in the environment, heavy metals pollution has become a critical issue and attracted considerable attentions because of both acute and chronic toxicity [1]. Heavy metals

have released to the environment by industrial manufacture such as pesticides, fertilizers, dyes, drugs, battery, tannery, fossil fuel, ceramic and glass industries printing [2,3]. Lead (Pb²⁺), as a heavy

*Corresponding author: Avvaru Praveen Kumar, Email: drkumar.kr@gmail.com

metal, exist as pollutant in soil and water. Lead should be removed from water because of its high toxicity, non-biodegradable nature and bioaccumulation in the food chain [4,5]. Pb^{2+} causes serious nervous system problems, gastrointestinal diseases, blood and brain disorders, and cancer [6,7]. To remove Pb^{2+} from wastewaters, several methods have been handled such as coagulation [8], floatation [9], precipitation [10], solvent extraction [11], adsorption [12] and ion exchange [13]. Adsorption, among the mentioned method, because of simplicity, and low cost is the most promising one [14,15]. Many different adsorbent have been applied to remove lead from wastewaters including zeolites [12], activated carbons [16], fly ash [17], and metal oxides [18].

Co_3O_4 , a p-type semiconductor, has many attractive properties including high catalytic activity [19], supercapacity [20], heavy metal removal [21], and gas sensing [22]. On the other hand, Zinc oxide (ZnO) is an n-type semiconductor with wide direct band gap (3.4 eV) [23] and various applications such as hydrogen storage [24], photocatalyst [25], piezoelectric sensor [26] and heavy metal removal [27]. Consequently, combination of these two significant metal oxides will expand their potential

application area.

Different synthetic method have been reported to produce nano Co_3O_4 - ZnO such as electro-spinning process [28], homogeneous precipitation method [29], plasma enhanced-chemical vapor deposition [30], and photochemical coating method [31]. Co_3O_4 - ZnO were used as photocatalyst for degradation of rhodamine B dye [28], piezoelectric transducer [32], and gas sensor [30]. Herein, we have synthesized nano Co_3O_4 -ZnO by simple and green gel combustion method. The fuel was used for combustion in this work is Sugar. This method has never been reported for the synthesis of such material previously. The nano Co_3O_4 -ZnO were characterized and the adsorption of Pb^{2+} on its surface was investigated. To prove the adsorption of lead on the surface of as synthesized samples we used EDAX and SEM analysis. Moreover, the concentrations of remained Pb^{2+} ions were also measured by atomic absorption spectroscopy (AAS).

2.1 Materials

Zinc nitrate hexahydrate, cobalt nitrate hexahydrate were used as precursors. Commercial sugar purchased from the local market was used as a fuel for combustion. lead nitrate solution was used for

adsorption, which was prepared by dissolving lead nitrate (Merck; >99%, LR grade).

2.2. Synthesis of Co₃O₄

Co₃O₄ was synthesized by the gel combustion method, which is used to synthesize ZnO nano structures, before [2]. Cobalt nitrate hexahydrate was applied as the cobalt precursor. 0.01 mol (2.91 g) of cobalt nitrate hexahydrate and 5 g of sugar were dissolved in 30 mL distilled water. The reaction mixture was placed on a hot plate at 250°C. During the heating process, water vapor and nitric gases were released and the gel is formed. The gel was then calcinated at 600°C for 2 hours and characterized for further use.

2.3 Synthesis of Co₃O₄- ZnO

To prepare ZnO-Co₃O₄ samples, different aqueous metal nitrate solutions were prepared by dissolving each cobalt nitrate and zinc nitrate in water at different ratio (5:5, 8:2, 7:3, and 9:1). After mixing the desired solution, 5 g of sugar was added to the mixture. The reaction mixture was then placed on a hot plate at 250°C. During the heating process, water vapor and nitric gases were released and the gel is formed. The prepared gel was then calcinated at 600°C for 2 hours and characterized for

further use.

2.4 Adsorption Studies of Pb on the Surface

0.125 gram of synthesized Co₃O₄ and each ZnO-Co₃O₄ samples were separately added to the 15 mL of 0.5 M lead nitrate solution taken in a 50 mL conical flask and the solution was shaken by mechanical shaker for three hours. Co₃O₄ and each ZnO-Co₃O₄ adsorbents were then filtered and filtrates was dried at 200°C. The dried powders were characterized SEM and EDAX analysis. The concentrations of remained Pb²⁺ ions in supernatant were also measured by atomic absorption spectroscopy (AAS) and the sample absorbance was measured. The adsorption efficiency (R%) were measured using the following equation:

$$R\% = \frac{C_0 - C_f}{C_f} \times 100$$

Where C_0 is the initial metal ions concentration (mg l⁻¹) and C_f the final Pb²⁺ concentration (mg l⁻¹).

3. Results and Discussions

3.1 X-ray diffraction (XRD) analysis

XRD of Co₃O₄ is represented in Figure 1a. The sample in Figure 1a having crystalline morphology with broad peaks match well with the Co₃O₄ JCPDS card 43-1003. The apparent peaks at 2θ values of 19.01, 31.22, 37.12, 38.95, 44.18, 55.87, 59.50, 65.48 and

77.23 correspond to the crystal planes of (111), (220), (311), (222), (400), (422), (511), (440) and (533) respectively, which confirms the formation of pure Co_3O_4 [28]. The crystal size of the sample was calculated by Scherrer equation. The average particle size of the cobalt oxide was

found to be 43.685 nm. XRD patterns of as synthesized Co_3O_4 -ZnO nanoparticles are shown in figure 1b-e. It is observable that ZnO peaks is presented on the patterns. The average particle size of Co_3O_4 -ZnO 9:1, 8:2, 7:3, and 5:5 are 35.023, 40.915, 46.600, and 52.950 respectively.

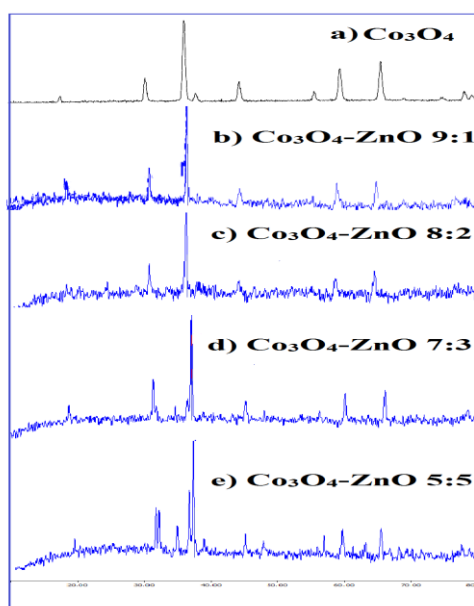


Fig. 1. XRD patterns of a) pure Co_3O_4 , b) Co_3O_4 -ZnO 9:1, c) Co_3O_4 -ZnO 8:2, d) Co_3O_4 -ZnO 7:3, and e) Co_3O_4 -ZnO 5:5.

3.2 Energy Dispersive X-Ray analysis (EDAX) Analysis

The EDX analyses results depict the presence of only cobalt and oxygen elements in the as-synthesized Co_3O_4 sample (Fig. 2(a)). The EDAX analysis data of the Co_3O_4 -ZnO indicate the presence of Zn atoms besides Co and O atoms, which

prove the samples, are properly synthesized (Fig. 2(b-e)). Moreover, it is clear that no other peak related to any other impurity has been detected in the EDAX, which confirms the synthetic process was carried out appropriately. Mass and atomic percentages of different elements is presented in table 1 (the rest are impurities).

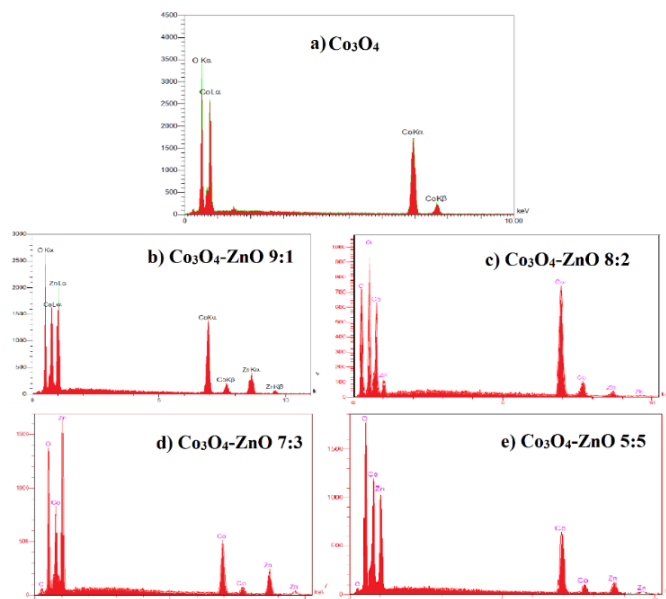


Fig. 2. EDAX spectra of a) pure Co_3O_4 , b) $\text{Co}_3\text{O}_4\text{-ZnO}$ 9:1, c) $\text{Co}_3\text{O}_4\text{-ZnO}$ 8:2, d) $\text{Co}_3\text{O}_4\text{-ZnO}$ 7:3, and e) $\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5

Table 1. EDAX results of the as-synthesized samples

Sample	Element content					
	weight%			atomic%		
	Co K	Zn K	O K	Co K	Zn K	O K
Co_3O_4	77.91	0	27.62	39.78	0	56.22
$\text{Co}_3\text{O}_4\text{-ZnO}$ 9:1	65.35	4.77	21.06	42.58	1.60	49.87
$\text{Co}_3\text{O}_4\text{-ZnO}$ 8:2	48.20	10.32	27.12	26.12	5.38	45.14
$\text{Co}_3\text{O}_4\text{-ZnO}$ 7:3	46.17	21.28	29.64	24.54	10.16	57.83
$\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5	35.17	39.49	23.97	21.22	21.48	53.26

The EDAX spectrum of the synthesized lead adsorbed samples were shown in Figure 3 (a-e). EDAX spectrums show just the presence of cobalt, zinc, lead and oxygen elements indicating the purity of both the adsorbent and adsorbate. By comparing Figure 2 (a) and Figure 3 (a), it is observable that two spectrum are approximately the same, showing that Co_3O_4 sample did not adsorb any lead. This similarity are also observable in figure 2 (b)

and 2(c), indicating the sample $\text{Co}_3\text{O}_4\text{-ZnO}$ 9:1 did not adsorb lead on the surface. The peaks found in between 2.5 to 3 Kev in Figure 3 (c-e) indicate the presence of lead on the surface of $\text{Co}_3\text{O}_4\text{-ZnO}$ 8:2, $\text{Co}_3\text{O}_4\text{-ZnO}$ 7:3, and $\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5. EDAX strongly proved the adsorption of Pb on the surface of $\text{Co}_3\text{O}_4\text{-ZnO}$ adsorbent. As can be seen in figure 3, by increasing the amount of ZnO on the structure of the samples, the adsorption of Pb on the surface increased

too. Mass and atomic percentages of (the rest are impurities).
different elements is presented in table 2

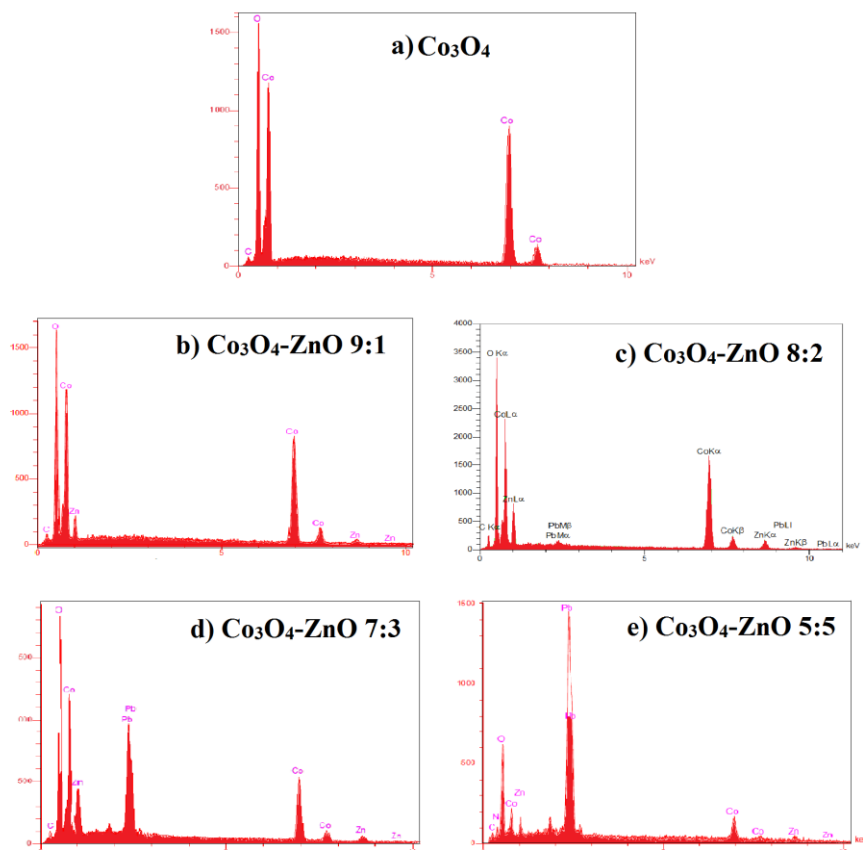


Fig. 3. EDAX spectra of Pb^{2+} adsorbed a) pure Co_3O_4 , b) Co_3O_4-ZnO 9:1, c) Co_3O_4-ZnO 8:2, d) Co_3O_4-ZnO 7:3, and e) Co_3O_4-ZnO 5:5.

Table 2 EDAX results of the as-synthesized samples after Pb^{2+} adsorption

Sample	Element content				Element content			
	weight%				atomic%			
	Co K	Zn K	O K	Pb K	Co K	Zn K	O K	Pb K
Co_3O_4	68.82	0	25.22	0	32.68	0	51.24	0
Co_3O_4-ZnO 9:1	63.45	5.47	25.68	0	40.28	2.90	55.67	0
Co_3O_4-ZnO 8:2	44.51	4.81	32.12	16.17	24.13	2.41	46.18	2.35
Co_3O_4-ZnO 7:3	39.19	6.76	34.18	24.57	15.87	3.20	66.17	3.67
Co_3O_4-ZnO 5:5	10.45	3.01	23.88	52.56	6.48	1.68	54.58	9.27

3.3 Scanning electron microscopy (SEM)

SEM was used to study the surface morphology of the synthesized samples. Figure 4 shows the SEM pictures of Co_3O_4 and Co_3O_4 -ZnO nanoparticles prepared by the gel combustion method. As shown in Figure 4, the synthesized particles are

relatively spherical. Besides, the synthesized nanoparticles are approximately homogeneous in nature. In the samples Co_3O_4 and Co_3O_4 -ZnO 9:1 aggregation were occurred however, the other samples are distributed properly.

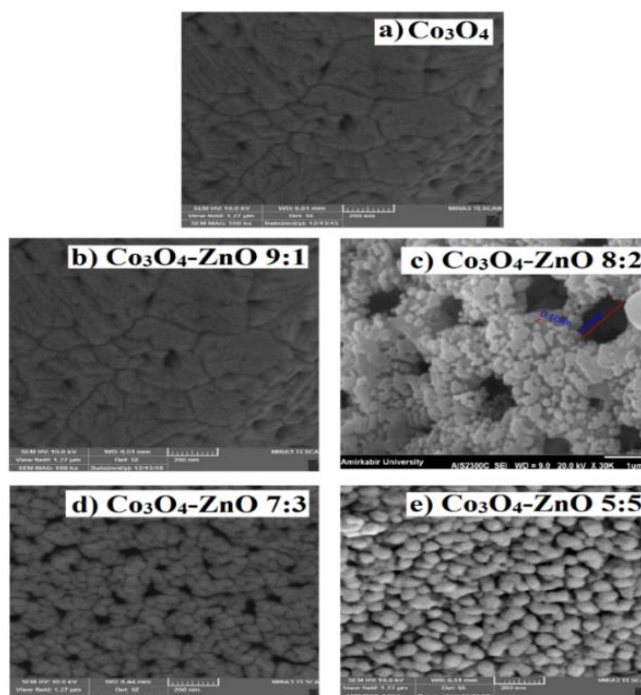


Fig. 4. SEM images of a) pure Co_3O_4 , b) Co_3O_4 -ZnO 9:1, c) Co_3O_4 -ZnO 8:2, d) Co_3O_4 -ZnO 7:3, and e) Co_3O_4 -ZnO 5:5.

Figure 5 depicts the SEM image of lead adsorbed Co_3O_4 and Co_3O_4 -ZnO nanoparticles. SEM images of Co_3O_4 and Co_3O_4 -ZnO 9:1 before and after adsorption are not different because the pores between particles are not reachable by lead (comparing figure 4 and 5 (a and b)). However, for the other Co_3O_4 -ZnO samples,

it is obvious that the distances between nanoparticles are covered after adsorption, which indicates the nucleating growth of lead on the surface of the adsorbent. These images help the confirmation of lead adsorption on the surface of as synthesized samples.

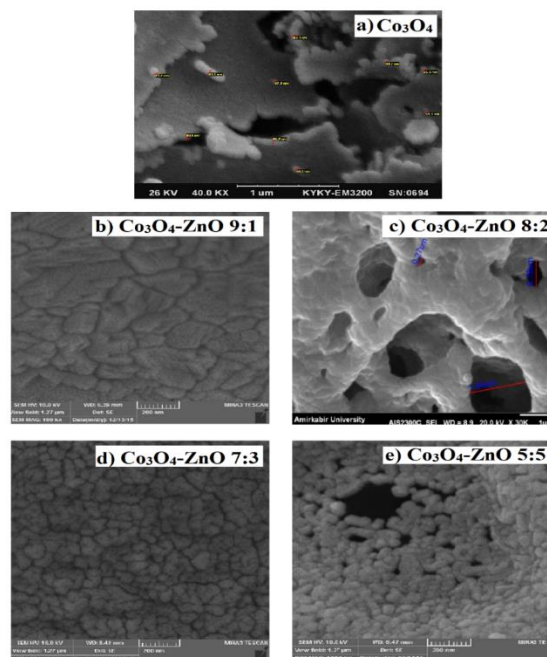


Fig. 5. SEM images of a) pure Co_3O_4 , b) $\text{Co}_3\text{O}_4\text{-ZnO}$ 9:1, c) $\text{Co}_3\text{O}_4\text{-ZnO}$ 8:2, d) $\text{Co}_3\text{O}_4\text{-ZnO}$ 7:3, and e) $\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5 after Pb^{2+} adsorption.

To study Pb^{2+} adsorption on the surface of $\text{Co}_3\text{O}_4\text{-ZnO}$ samples, the concentrations of remained Pb^{2+} ions in supernatant were also measured by atomic absorption spectroscopy (AAS) and the sample absorbance was measured. The results of these experiments were shown in table 3. It seems that pure Co_3O_4 is not able to act as dependent to remove lead from solution. As

can be seen, adsorption efficiency increase with increase in ZnO in the $\text{Co}_3\text{O}_4\text{-ZnO}$ structures, for pure Co_3O_4 the adsorption efficiency was 0% and further increase in the ZnO the efficiency increase to 77.17% for $\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5. Consequently, $\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5 is the best adsorbent of Pb^{2+} compared to other adsorbents studied in this research.

Table 3 Adsorption efficiency of as synthesized samples for lead removal

adsorbent	Adsorption efficiency
Co_3O_4	0
$\text{Co}_3\text{O}_4\text{-ZnO}$ 9:1	0
$\text{Co}_3\text{O}_4\text{-ZnO}$ 8:2	70.95
$\text{Co}_3\text{O}_4\text{-ZnO}$ 7:3	74.41
$\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5	77.17

Table 4 compares the characteristic data of the current method with other methods for adsorption of Pb in different samples [2,32–34]. As can be seen, the result is better or in some cases comparable to the other

adsorbents. It can be inferred from this comparison that $\text{Co}_3\text{O}_4\text{-ZnO}$ have a high lead adsorption capacity.

Table 4. Adsorption capacity of $\text{Co}_3\text{O}_4\text{-ZnO}$ and other recently reported adsorbents.

order	Adsorbent	Adsorption capacity (mg/g)	Route followed	reference
1	ZnO NPs	19.65	Gel combustion	[2]
2	CuO NPs	188.7	Sol-gel	[33]
3	ZnO/MMT nanocomposite	34.84	Heat method	[34]
4	Pretreated clinoptilolite	122.4	-	[35]
5	$\text{Co}_3\text{O}_4\text{-ZnO}$	185.2	Gel combustion	This work

4. Conclusion

In this research, nano $\text{Co}_3\text{O}_4\text{-ZnO}$ have been successfully synthesized by a simple and green gel combustion method followed by calcination at 600 °C. Sugar was used as fuel for combustion in this work. This study clearly establishes that $\text{Co}_3\text{O}_4\text{-ZnO}$ is an efficient adsorbent for Pb (II) removal from aqueous solution. EDAX strongly proved the adsorption of lead on the surface of $\text{Co}_3\text{O}_4\text{-ZnO}$ adsorbent. The SEM images also help the confirmation of lead adsorption on the surface of as synthesized samples. The obtained results of AAS show the adsorption efficiency increase with incensement of ZnO in the $\text{Co}_3\text{O}_4\text{-ZnO}$ structures. $\text{Co}_3\text{O}_4\text{-ZnO}$ 5:5 is the best adsorbent of Pb^{2+} compared to the other

adsorbents studied in this research. In comparison with recent studies, in this work the adsorbent was synthesized by method that is more convenient with better or in some cases comparable results for lead removal.

Acknowledgment

The authors are grateful to Research affairs of Shahid Bahonar University of Kerman for the financial support.

References

1. Islam A, Ahmad H, Zaidi N, Kumar S (2014) ACS applied materials & interfaces 6: 13257-13265.
2. Venkatesham V, Madhu G, Satyanarayana S, Preetham H (2013) Procedia Engineering 51: 308-313.

3. Kılıc M, Kırbıyık C, Çepelioğullar Ö, Pütün AE (2013) Applied Surface Science 283: 856-862.
4. Pardo R, Herguedas M, Barrado E, Vega M (2003) Analytical and bioanalytical chemistry 376: 26-32.
5. Needleman H (2004) Annu Rev Med 55: 209-222.
6. Savio M, Parodi B, Martinez LD, Smichowski P, Gil RA (2011) Talanta 85: 245-251.
7. Fayazi M, Taher MA, Afzali D, Mostafavi A, Ghanei-Motlagh M (2016) Materials Science and Engineering: C 60: 365-373.
8. Pang FM, Kumar P, Teng TT, Omar AM, Wasewar KL (2011) Journal of the Taiwan Institute of Chemical Engineers 42: 809-815.
9. Thackston EL, Wilson DJ, Hanson JS, Miller Jr DL (1980) Journal (Water Pollution Control Federation): 317-328.
10. Macchi G, Marani D, Pagano M, Bagnuolo G (1996) Water Research 30: 3032-3036.
11. Shah D, Phadke A, Kocher W (1995) Journal of the Air & Waste Management Association 45: 150-155.
12. Günay A, Arslankaya E, Tosun I (2007) Journal of Hazardous Materials 146: 362-371.
13. Ahmed S, Chughtai S, Keane MA (1998) Separation and purification technology 13: 57-64.
14. Zamboulis D, Peleka EN, Lazaridis NK, Matis KA (2011) Journal of Chemical Technology and Biotechnology 86: 335-344.
15. Halimi M, Nasrabadi M, Soleamani N, Rouhani N (2018) Asian Journal of Nanoscience and Materials 1: 19-24.
16. Goel J, Kadirvelu K, Rajagopal C, Garg VK (2005) Journal of hazardous materials 125: 211-220.
17. Gupta VK, Ali I (2004) Journal of colloid and interface science 271: 321-328.
18. Han R, Zou W, Zhang Z, Shi J, Yang J (2006) Journal of Hazardous Materials 137: 384-395.
19. Yang P, Cui Q, Zu Y, Liu X, Lu G, Wang Y (2015) Catalysis Communications 66: 55-59.
20. Liao Q, Li N, Jin S, Yang G, Wang C (2015) Acs Nano 9: 5310-5317.
21. Hu JS, Zhong LS, Song WG, Wan LJ (2008) Advanced Materials 20: 2977-2982.
22. Vetter S, Haffer S, Wagner T, Tiemann M (2015) Sensors and Actuators B: Chemical 206: 133-138.
23. Klingshirn C (2007) ChemPhysChem 8: 782-803.
24. Wan Q, Lin C, Yu X, Wang T (2004) Applied Physics Letters 84: 124-126.
25. He L, Tong Z, Wang Z, Chen M, Huang N, Zhang W (2018) Journal of colloid and interface science 509: 448-456.
26. Bhatia D, Sharma H, Meena R, Palkar V (2016) Sensing and Bio-Sensing Research 9: 45-52.
27. Kumar KY, Muralidhara H, Nayaka YA, Balasubramanyam J, Hanumanthappa H (2013) Powder technology 239: 208-216.
28. Kanjwal MA, Sheikh FA, Barakat NA, Li X, Kim HY, Chronakis IS (2011) Journal of Nanoengineering and nanomanufacturing 1: 196-202.
29. Sharma RK, Ghose R (2016) Journal of Alloys and Compounds 686: 64-73.
30. Bekermann D, Gasparotto A, Barreca D, Maccato C, Comini E, Sada C, Sberveglieri G, Devi A, Fischer R (2012) ACS applied materials & interfaces 4: 928-934.
31. Tak Y, Yong K (2008) The Journal of Physical Chemistry C 112: 74-79.
32. Hu Y-C, Lee T-H, Chang P-Z, Su P-C (2015) Thin Solid Films 584: 112-115.
33. Bhanjana G, Dilbaghi N, Kim K-H, Kumar S (2017) Journal of Molecular Liquids 244: 506-511.
34. Sani HA, Ahmad MB, Hussein MZ, Ibrahim NA, Musa A, Saleh TA (2017) Process Safety and Environmental Protection 109: 97-105.

35. Günay A, Arslankaya E, Tosun I (2007)
Journal of Hazardous Materials 146: 362-
371.

How to cite this manuscript: Iran Sheikhshoae*, Azimeh Rezazadeh, Samaneh Ramezanzpour. Removal of Pb (II) from aqueous solution by gel combustion derived nano Co₃O₄- ZnO. Asian Journal of Nanoscience and Materials, 2018, **1** (4), 271-281.